

Institute for
Interlaboratory Studies

Results of Proficiency Test OPP and Other Preservatives in Leather/Footwear April 2022

Organized by: Institute for Interlaboratory Studies
Spijkenisse, the Netherlands

Authors: ing. A. Ouwerkerk & Mrs. E.R. Montenij-Bos
Correctors: ing. R.J. Starink & ing. G.A. Oosterlaken-Buijs
Approved by: ing. A.S. Noordman-de Neef

Report: iis22A07

July 2022

CONTENTS

1	INTRODUCTION	3
2	SET UP	3
2.1	QUALITY SYSTEM.....	3
2.2	PROTOCOL.....	3
2.3	CONFIDENTIALITY STATEMENT	4
2.4	SAMPLES	4
2.5	ANALYZES	5
3	RESULTS	5
3.1	STATISTICS	6
3.2	GRAPHICS	6
3.3	Z-SCORES	7
4.0	EVALUATION	8
4.1	EVALUATION PER COMPONENT	8
4.2	PERFORMANCE EVALUATION FOR THE GROUP OF LABORATORIES.....	9
4.3	COMPARISON OF THE PROFICIENCY TEST OF APRIL 2022 WITH PREVIOUS PTS	9
4.4	EVALUATION OF THE ANALYTICAL DETAILS.....	10
5	DISCUSSION.....	10
6	CONCLUSION.....	11
Appendices:		
1.	Data, statistical and graphic results	12
2.	Other reported Preservatives.....	15
3.	Analytical details	16
4.	Number of participants per country.....	17
5.	Abbreviations and literature	18

1 INTRODUCTION

Since 1990 many countries have adopted environmental standards and requirements restricting the use of harmful chemicals in the production of textiles and clothing. Laws and regulations impose some of these standards and requirements. In addition to mandatory environmental standards and requirements for leather there are some Ecolabelling schemes imposing environmental requirements for textile and leather products on a voluntary basis. Well-known Ecolabelling organizations are OEKO-TEX® and Bluesign®.

Since 2018 the Institute for Interlaboratory Studies (iis) organizes a proficiency scheme for the determination of Ortho-Phenylphenol (OPP) and other preservatives in Leather/Footwear every year. During the annual proficiency testing program 2021/2022 it was decided to continue the proficiency test for the determination of OPP and Other Preservatives in Leather/Footwear.

In this interlaboratory study 39 laboratories in 17 countries registered for participation, see appendix 4 for the number of participants per country. In this report the results of the OPP and Other Preservatives in Leather/Footwear proficiency test are presented and discussed. This report is also electronically available through the iis website www.iisnl.com.

2 SET UP

The Institute for Interlaboratory Studies (iis) in Spijkenisse, the Netherlands, was the organizer of the proficiency test (PT). Sample analyzes for fit-for-use and homogeneity testing were subcontracted to an ISO/IEC17025 accredited laboratory. It was decided to send one leather sample containing some preservatives of 3 grams labelled #22590.

The participants were requested to report rounded and unrounded test results. The unrounded test results were preferably used for statistical evaluation.

2.1 QUALITY SYSTEM

The Institute for Interlaboratory Studies in Spijkenisse, the Netherlands, has implemented a quality system based on ISO/IEC17043:2010. This ensures strict adherence to protocols for sample preparation and statistical evaluation and 100% confidentiality of participant's data. Feedback from the participants on the reported data is encouraged and customer's satisfaction is measured on regular basis by sending out questionnaires.

2.2 PROTOCOL

The protocol followed in the organisation of this proficiency test was the one as described for proficiency testing in the report 'iis Interlaboratory Studies: Protocol for the Organisation, Statistics and Evaluation' of June 2018 (iis-protocol, version 3.5). This protocol is electronically available through the iis website www.iisnl.com, from the FAQ page.

2.3 CONFIDENTIALITY STATEMENT

All data presented in this report must be regarded as confidential and for use by the participating companies only. Disclosure of the information in this report is only allowed by means of the entire report. Use of the contents of this report for third parties is only allowed by written permission of the Institute for Interlaboratory Studies. Disclosure of the identity of one or more of the participating companies will be done only after receipt of a written agreement of the companies involved.

2.4 SAMPLES

A batch of black leather containing OPP was obtained from a third party. The batch was grinded into small pieces. After homogenization 70 plastic bags were filled with approximately 3 grams each and labelled #22590.

The homogeneity of the subsamples was checked by determination of OPP by an in house test method on 10 stratified randomly selected subsamples.

	OPP in mg/kg
sample #22590-1	281.4
sample #22590-2	288.3
sample #22590-3	277.7
sample #22590-4	285.6
sample #22590-5	235.0
sample #22590-6	242.2
sample #22590-7	242.7
sample #22590-8	278.1
sample #22590-9	270.4
sample #22590-10	267.6

Table 1: homogeneity test results of subsamples #22590

From the above test results the relative standard deviation (RSD) was calculated and compared with 0.3 times the average relative standard deviation derived from iis PTs 2018-2021 in agreement with the procedure of ISO13528, Annex B2 in the next table.

	OPP
RSD (observed)	7%
reference method	iis PTS
0.3 x RSD (reference method)	7%

Table 2: evaluation of the relative standard deviation of subsamples #22590

The calculated relative standard deviation is in agreement with 0.3 times the average relative standard obtained from the previous iis PTs. Therefore, homogeneity of the subsamples was assumed.

To each of the participants one sample labelled #22590 was sent on March 30, 2022.

2.5 ANALYZES

The participants were requested to determine the concentrations of Ortho-Phenylphenol (OPP), 2-(Thiocyanomethylthio)-Benzothiazole (TCMTB), 4-Chloro-3-Methylphenol (PCMC), 2-Octylisothiazol-3(2H)-one (OIT), Triclosan (TCS) and Other Preservatives.

To ensure homogeneity it was requested not to use less than 0.5 gram per determination. It was also requested to report if the laboratory was accredited to determine the requested components and to report some analytical details.

It was explicitly requested to treat the sample as if it was a routine sample, but not to age nor dry the sample nor to determine volatile matter. The amount of sample was not sufficient to allow aging and/or determine the volatile matter content.

It was requested to report the test results using the indicated units on the report form and not to round the results, but report as much significant figures as possible. It was also requested not to report 'less than' test results, which are above the detection limit, because such test results cannot be used for meaningful statistical evaluations.

To get comparable test results a detailed report form and a letter of instructions are prepared. On the report form the reporting units are given as well as the reference test methods (when applicable) that will be used during the evaluation. The detailed report form and the letter of instructions are both made available on the data entry portal www.kpmd.co.uk/sgs-iis-cts/. The participating laboratories are also requested to confirm the sample receipt on this data entry portal. The letter of instructions can also be downloaded from the iis website www.iisnl.com.

3 RESULTS

During five weeks after sample dispatch, the test results of the individual laboratories were gathered via the data entry portal www.kmpd.co.uk/sgs-iis-cts/. The reported test results are tabulated per determination in appendices 1 and 2 of this report. The laboratories are presented by their code numbers.

Directly after the deadline, a reminder was sent to those laboratories that had not reported test results at that moment. Shortly after the deadline, the available test results were screened for suspect data. A test result was called suspect in case the Huber Elimination Rule (a robust outlier test) found it to be an outlier. The laboratories that produced these suspect data were asked to check the reported test results (no reanalyzes). Additional or corrected test results are used for the data analysis and the original results are placed under 'Remarks' in the result tables in appendices 1 and 2. Test results that came in after the deadline were not taken into account in this screening for suspect data and thus these participants were not requested for checks.

3.1 STATISTICS

The protocol followed in the organization of this proficiency test was the one as described for proficiency testing in the report 'iis Interlaboratory Studies: Protocol for the Organisation, Statistics and Evaluation' of June 2018 (iis-protocol, version 3.5).

For the statistical evaluation the *unrounded* (when available) figures were used instead of the rounded test results. Test results reported as '<...>' or '>...>' were not used in the statistical evaluation.

First, the normality of the distribution of the various data sets per determination was checked by means of the Lilliefors-test, a variant of the Kolmogorov-Smirnov test and by the calculation of skewness and kurtosis. Evaluation of the three normality indicators in combination with the visual evaluation of the graphic Kernel density plot, lead to judgement of the normality being either 'unknown', 'OK', 'suspect' or 'not OK'. After removal of outliers, this check was repeated. If a data set does not have a normal distribution, the (results of the) statistical evaluation should be used with due care.

The assigned value is determined by consensus based on the test results of the group of participants after rejection of the statistical outliers and/or suspect data.

According to ISO13528 all (original received or corrected) results per determination were submitted to outlier tests. In the iis procedure for proficiency tests, outliers are detected prior to calculation of the mean, standard deviation and reproducibility. For small data sets, Dixon (up to 20 test results) or Grubbs (up to 40 test results) outlier tests can be used. For larger data sets (above 20 test results) Rosner's outlier test can be used. Outliers are marked by D(0.01) for the Dixon's test, by G(0.01) or DG(0.01) for the Grubbs's test and by R(0.01) for the Rosner's test. Stragglers are marked by D(0.05) for the Dixon's test, by G(0.05) or DG(0.05) for the Grubbs' test and by R(0.05) for the Rosner's test. Both outliers and stragglers were not included in the calculations of averages and standard deviations.

For each assigned value the uncertainty was determined in accordance with ISO13528. Subsequently the calculated uncertainty was evaluated against the respective requirement based on the target reproducibility in accordance with ISO13528. In this PT, the criterion of ISO13528, paragraph 9.2.1 was met for all evaluated tests, therefore, the uncertainty of all assigned values may be negligible and need not be included in the PT report.

Finally, the reproducibilities were calculated from the standard deviations by multiplying them with a factor of 2.8.

3.2 GRAPHICS

In order to visualize the data against the reproducibilities from literature, Gauss plots were made, using the sorted data for one determination (see appendix 1). On the Y-axis the reported test results are plotted. The corresponding laboratory numbers are on the X-axis. The straight horizontal line presents the consensus value (a trimmed mean). The four striped lines, parallel to the consensus value line, are the +3s, +2s, -2s and -3s target reproducibility limits of the selected reference test method. Outliers and other data, which were excluded from the calculations, are represented as a cross. Accepted data are represented as a triangle.

Furthermore, Kernel Density Graphs were made. This is a method for producing a smooth density approximation to a set of data that avoids some problems associated with histograms. Also, a normal Gauss curve (dotted line) was projected over the Kernel Density Graph (smooth line) for reference. The Gauss curve is calculated from the consensus value and the corresponding standard deviation.

3.3 Z-SCORES

To evaluate the performance of the participating laboratories the z-scores were calculated. As it was decided to evaluate the performance of the participants in this proficiency test (PT) against the literature requirements (derived from e.g. ISO or ASTM test methods), the z-scores were calculated using a target standard deviation. This results in an evaluation independent of the variation in this interlaboratory study.

The target standard deviation was calculated from the literature reproducibility by division with 2.8. In case no literature reproducibility was available, other target values were used, like Horwitz or an estimated reproducibility based on former iis proficiency tests.

When a laboratory did use a test method with a reproducibility that is significantly different from the reproducibility of the reference test method used in this report, it is strongly advised to recalculate the z-score, while using the reproducibility of the actual test method used, this in order to evaluate whether the reported test result is fit-for-use.

The z-scores were calculated according to:

$$z_{(\text{target})} = (\text{test result} - \text{average of PT}) / \text{target standard deviation}$$

The $z_{(\text{target})}$ scores are listed in the test result tables in appendix 1.

Absolute values for $z < 2$ are very common and absolute values for $z > 3$ are very rare. The usual interpretation of z-scores is as follows:

	$ z < 1$	good
1 <	$ z < 2$	satisfactory
2 <	$ z < 3$	questionable
3 <	$ z $	unsatisfactory

4 EVALUATION

In this proficiency test some problems were encountered with the dispatch of the samples due to COVID-19 pandemic. Therefore, the reporting time on the data entry portal was extended with another week. Six participants reported test results after the extended reporting date and two other participants did not report any test results. Not all participants were able to report all tests requested.

In total 37 participants reported 91 numerical test results. Observed were 0 outlying test results, which is 0%. In proficiency studies, outlier percentages of 3% - 7.5% are quite normal.

Not all data sets proved to have a normal Gaussian distribution. These are referred to as “not OK” or “suspect”. The statistical evaluation of these data sets should be used with due care, see also paragraph 3.1.

4.1 EVALUATION PER COMPONENT

In this section the reported test results are discussed per component. The test methods which were used by the various laboratories were taken into account for explaining the observed differences when possible and applicable. These test methods are also in the tables together with the original data in appendix 1. The abbreviations, used in these tables, are explained in appendix 5.

The official test method for the determination of OPP and other preservatives in Leather/Footwear is considered to be test method ISO13365-1 or -2. Regretfully test method ISO13365-1 or -2 does not provide precision data for OPP or any other preservatives. When no test method reproducibility is known the target reproducibility is in general estimated using the Horwitz equation. However, in 2016 iis investigated the reproducibilities of the determination of OPP in textile over 18 determinations in iis PTs conducted from 2004 until 2014. It was observed in these PTs that the estimated reproducibility based on the Horwitz equation was very strict. Therefore, a new target reproducibility on base of the iis PTs was determined and described in iis memo 1601. Although iis memo 1601 is based on iis PTs of OPP in Textile it is decided to use the estimated iis target reproducibility also for the determination of OPP in Leather. Furthermore, it is decided to use the estimated iis target reproducibility for other preservatives determined in Leather as well.

OPP: This determination was not problematic. No statistical outliers were observed. The calculated reproducibility is in agreement with the target reproducibility as derived from iis memo 1601.

PCMC: The determination was not problematic. No statistical outliers were observed. The calculated reproducibility is in agreement with the target reproducibility as derived from iis memo 1601.

OIT: The determination was not problematic. No statistical outliers were observed. The calculated reproducibility is in agreement with the target reproducibility as derived from iis memo 1601.

The majority of the participants agreed on a concentration near or below the limit of detection for all other requested Preservatives mentioned in paragraph 2.5. Therefore, no z-scores are calculated. The reported test results can be found in appendix 2.

4.2 PERFORMANCE EVALUATION FOR THE GROUP OF LABORATORIES

A comparison has been made between the reproducibility as declared by the reference test method and the reproducibility as found for the group of participating laboratories. The number of significant test results, the average, the calculated reproducibility ($2.8 \times$ standard deviation) and the target reproducibility derived from previous iis PTs are presented in the next table.

Component	unit	n	average	2.8 * sd	R(target)
OPP	mg/kg	37	226.9	103.3	102.9
PCMC	mg/kg	32	73.8	28.8	39.6
OIT	mg/kg	22	10.0	7.9	7.3

Table 3: reproducibilities of preservatives on sample #22590

Without further statistical calculations it can be concluded that there is a good compliance of the group of participants with the target reproducibility of the reference method.

4.3 COMPARISON OF THE PROFICIENCY TEST OF APRIL 2022 WITH PREVIOUS PTS

	April 2022	May 2021	May 2020	May 2019	April 2018
Number of reporting laboratories	37	34	32	38	55
Number of test results	91	102	59	89	75
Number of statistical outliers	0	5	0	5	2
Percentage of statistical outliers	0%	4.9%	0%	5.6%	2.7%

Table 4: comparison with previous proficiency tests

In proficiency tests, outlier percentages of 3% - 7.5% are quite normal.

The performance of the determinations of the proficiency tests was compared, expressed as relative standard deviation (RSD) of the PTs, in the next table.

Component	April 2022	May 2021	May 2020	2018- 2019	Target *)
OPP	16%	14%	15%	21-23%	14-24%
TCMTB	n.e.	30%	n.e.	n.e.	14-24%
PCMC	14%	16%	26%	15-16%	14-24%
OIT	28%	25%	n.e.	39%	14-24%

Table 5: development of uncertainties over the years

*) Concentration range 600-15 mg/kg respectively

The uncertainties observed in this PT are in line with previous iis PTs.

4.4 EVALUATION OF THE ANALYTICAL DETAILS

Test method ISO13365-1:2020 describes a test method by Acetonitrile solvent extraction for the determination of the total content (solvent extractible) of the preservatives in leather by liquid chromatography. Test method ISO13365-2:2020 describes a test method by artificial perspiration solution aqueous extraction for the determination of the aqueous extractable preservatives in leather by liquid chromatography.

About 60% of the reporting participants mentioned to use ISO13365-1:2020 and about 16% mentioned to use ISO13365:2011 (previous version of ISO13365-1:2020). None of the participants mentioned to use test method ISO13365-2:2020.

Some analytical details were requested, see appendix 3 for the reported answers. Based on the answers given by the participants the following can be summarized:

- About 75% of the participants mentioned that they are accredited for the determination of the reported components.
- About 85% of the participants used the sample as received.
- Allmost all participants did use a test portion between 0.5 and 1 grams. One participant used 2 grams.

As the majority of the group participants follow the same analytical procedures and the performances of the determinations are in line with the target reproducibilities no separate statistical analysis has been performed.

5 DISCUSSION

In the next table the limits of the OEKO-TEX® Leather standard is given.

Component	Baby in mg/kg	Direct skin contact in mg/kg	No direct skin contact in mg/kg	Decoration material in mg/kg
OPP	<250	<750	<750	<750
TCMTB	<250	<500	<500	<500
PCMC	<150	<300	<300	<300
OIT	<50	<100	<100	<100

Table 6: OEKO-TEX® Ecolabelling Standard and Requirements for leathers in EU

For the determination of OPP and other Preservatives almost all participants would have accepted the sample for all classes of the OEKO-TEX® standard for Leather. Seven participants would have rejected the leather for baby.

Bluesign has two lists. A Bluesign® Systems Substances List (BSSL) and the Bluesign® Restricted List (RSL). The BSSL contains all chemicals that are restricted or suspected to be restricted and are therefore monitored. The RSL is an extract of the BSSL and contains the restricted chemicals with consumer safety limits. The Bluesign RSL mentions only a safety limit for OPP (see table 7).

Component	Class A Next to skin and Baby mg/kg	Class B Occasional skin contact mg/kg	Class C No skin contact mg/kg
OPP	<50	<100	<200

Table 7: Product classes specific limit values, Bluesign® RSL list

For OPP almost all participants would have rejected the leather for all classes of the RSL list of the Bluesign®. Seven participants would have accepted the leather for class C.

6 CONCLUSION



It can be concluded that the majority of the participants had no problems with the determination of OPP and other Preservatives in the sample in this PT.

Each participating laboratory will have to evaluate its performance in this study and decide about any corrective actions if necessary. Therefore, participation on a regular basis in this scheme could be helpful to improve the performance and thus increase of the quality of the analytical results.

APPENDIX 1

Determination of Ortho-Phenylphenol (OPP) on sample #22590; results in mg/kg



lab	method	value	mark	z(targ)	remarks
551	§64 LFGB,B82.02.8	319.266		2.51	
623	ISO13365:2011	276.26		1.34	
2115	ISO13365-1:2020	224.9		-0.05	
2129	ISO13365:2011	229.702		0.08	
2132	ISO13365-1:2020	216		-0.30	
2247	ISO13365:2011	228.12		0.03	
2250	In house	234.6		0.21	
2265	DIN50009	222.0		-0.13	
2293		-----		-----	
2310	ISO13365-1:2020	210		-0.46	
2311	ISO13365-1:2020	203.175		-0.65	
2330	ISO17070:2015	295.103		1.86	
2352	ISO13365-1:2020	226.6		-0.01	
2358	ISO13365-1:2020	213.49		-0.36	
2363		-----		-----	
2365	ISO13365-1:2020	201.74		-0.68	
2370	ISO13365-1:2020	227		0.00	
2375	ISO13365-1:2020	220		-0.19	
2386	In house	235.636		0.24	
2390	In house	202.98		-0.65	
2455	ISO13365-1:2020	211.788		-0.41	
2561	ISO13365-1:2020	227.6498		0.02	
2590	ISO13365-1:2020	259.444		0.89	
2602	ISO13365-1:2020	244.963		0.49	
2695	ISO13365:2011	179.618	C	-1.29	first reported 309.031
2711	In house	300.9		2.01	
2723	ISO13365-1:2020	256		0.79	
2737	ISO13365-1:2020	206.259		-0.56	
2756	ISO13365-1:2020	249.50		0.62	
2806	ISO13365-1:2020	159.3		-1.84	
2826	ISO13365-1:2020	196.5		-0.83	
2959	ISO13365-1:2020	196.53		-0.83	
3116	ISO13365-1:2020	212.9		-0.38	
3154	ISO13365:2011	183.087		-1.19	
3172	ISO13365-1:2020	209.85		-0.46	
3197	ISO13365-1:2020	188.2	C	-1.05	first reported 303.56
3210	In house	218.03		-0.24	
3228	ISO13365:2011	191		-0.98	
3237	In house	316.39		2.44	
normality		OK			
n		37			
outliers		0			
mean (n)		226.8779			
st.dev. (n)		36.89256	RSD = 16%		
R(calc.)		103.2992			
st.dev. (iis memo 1601)		36.74355			
R(iis memo 1601)		102.8820			

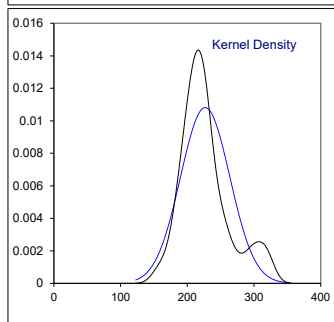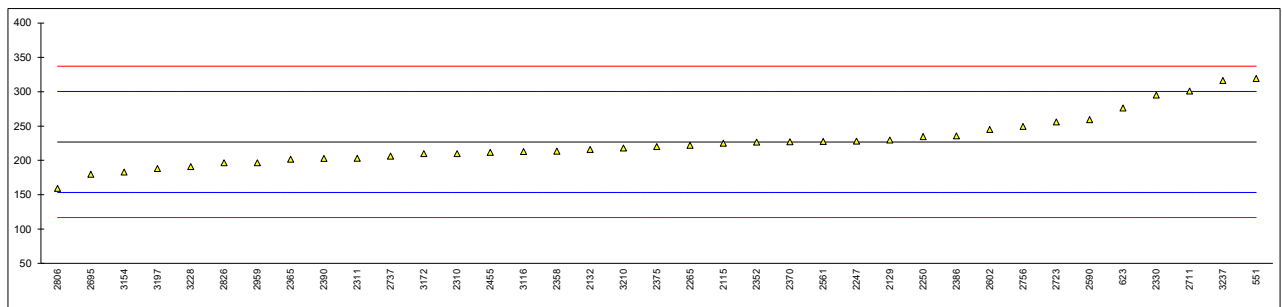

Determination of 4-Chloro-3-Methylphenol (PCMC) on sample #22590; results in mg/kg

lab	method	value	mark	z(targ)	remarks
551	§64 LFGB,B82.02.8	47.391		-1.87	
623	ISO13365:2011	75.28		0.11	
2115	ISO13365-1:2020	86.6		0.91	
2129	ISO13365:2011	59.849		-0.99	
2132	ISO13365-1:2020	71.6		-0.15	
2247	ISO13365:2011	55.85		-1.27	
2250	In house	76.8		0.21	
2265		----		----	
2293		----		----	
2310	ISO13365-1:2020	74.8		0.07	
2311	ISO13365-1:2020	73.813		0.00	
2330	ISO17070:2015	Not applicable		----	
2352	ISO13365-1:2020	74.7		0.06	
2358	ISO13365-1:2020	72.996		-0.06	
2363		----		----	
2365	ISO13365-1:2020	75.02		0.09	
2370	ISO13365-1:2020	84.7		0.77	
2375	ISO13365-1:2020	72		-0.13	
2386		----		----	
2390	In house	61.77		-0.85	
2455	ISO13365-1:2020	81.330		0.53	
2561	ISO13365-1:2020	77.03717		0.23	
2590	ISO13365-1:2020	60.882		-0.91	
2602	ISO13365-1:2020	89.322		1.10	
2695	ISO13365:2011	79.478		0.40	
2711	In house	97.0		1.64	
2723	ISO13365-1:2020	92		1.29	
2737	ISO13365-1:2020	77.324		0.25	
2756		----		----	
2806	ISO13365-1:2020	79.5		0.40	
2826	ISO13365-1:2020	70.98		-0.20	
2959	ISO13365-1:2020	69.53		-0.30	
3116	ISO13365-1:2020	70.77		-0.21	
3154	ISO13365:2011	75.108		0.09	
3172	ISO13365-1:2020	66.664		-0.50	
3197	ISO13365-1:2020	74.6	C	0.06	first reported 121.32
3210	In house	72.64		-0.08	
3228	ISO13365:2011	63.9		-0.70	
3237		----		----	



normality OK
 n 32
 outliers 0
 mean (n) 73.7886
 st.dev. (n) 10.27754 RSD = 14%
 R(calc.) 28.7771
 st.dev.(iis memo 1601) 14.14323
 R(iis memo 1601) 39.6010

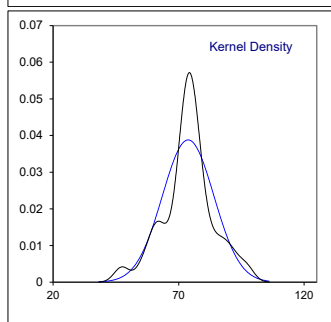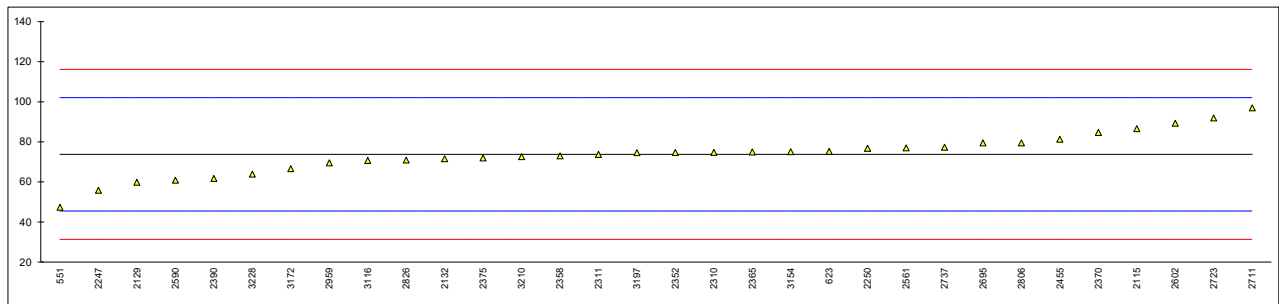

Determination of 2-Octylisothiazol-3(2H)-one (OIT) on sample #22590; results in mg/kg

lab	method	value	mark	z(targ)	remarks
551		----		----	
623	ISO13365:2011	7.74		-0.88	
2115	ISO13365-1:2020	11.61		0.61	
2129	ISO13365:2011	<10		----	
2132	ISO13365-1:2020	Not detected		----	
2247	ISO13365:2011	14.90		1.88	
2250	In house	16.4		2.45	
2265		----		----	
2293		----		----	
2310	ISO13365-1:2020	8.04		-0.77	
2311	ISO13365-1:2020	7.341		-1.04	
2330	ISO17070:2015	Not applicable		----	
2352	ISO13365-1:2020	8.2		-0.71	
2358	ISO13365-1:2020	not detected		----	
2363		----		----	
2365	ISO13365-1:2020	7.58		-0.95	
2370	ISO13365-1:2020	10.7		0.26	
2375	ISO13365-1:2020	8.5		-0.59	
2386		----		----	
2390	In house	not analyzed		----	
2455		----		----	
2561	ISO13365-1:2020	10.80884		0.30	
2590		----		----	
2602	ISO13365-1:2020	7.858		-0.84	
2695	ISO13365:2011	12.631		1.00	
2711	In house	not detected		----	
2723	ISO13365-1:2020	16		2.30	
2737	ISO13365-1:2020	9.056		-0.38	
2756		----		----	
2806	ISO13365-1:2020	12.1		0.80	
2826	ISO13365-1:2020	6.890		-1.21	
2959	ISO13365-1:2020	8.17		-0.72	
3116		----		----	
3154	ISO13365:2011	8.645		-0.54	
3172	ISO13365-1:2020	8.856		-0.45	
3197	ISO13365-1:2020	10.35		0.12	
3210	In house	<40		----	
3228	ISO13365:2011	8.37		-0.64	
3237		----		----	

normality suspect
n 22
outliers 0
mean (n) 10.0339
st.dev. (n) 2.82677 RSD = 28%
R(calc.) 7.9150
st.dev.(iis memo 1601) 2.59422
R(iis memo 1601) 7.2638

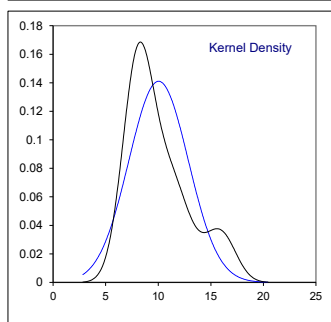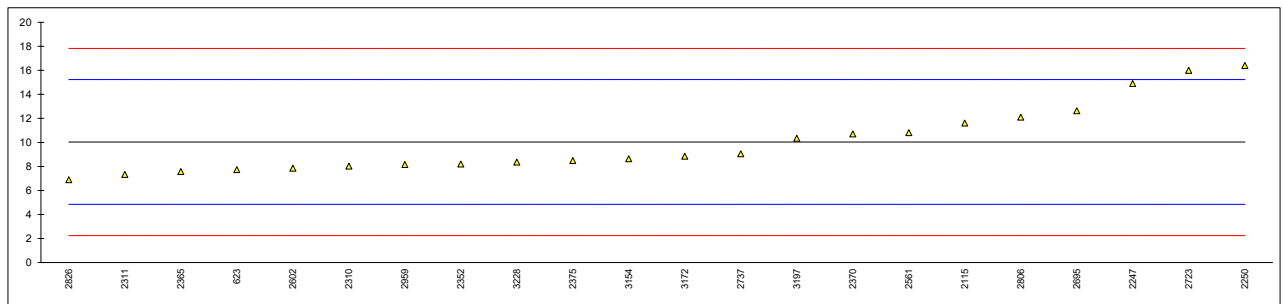

APPENDIX 2 Other reported Preservatives

lab	2-(Thiocyanomethylthio)-Benzothiazole (TCMTB)	Triclosan	Other Preservatives
551	----	----	----
623	2.25	Not Detected	Not Detected
2115	----	----	----
2129	<10	<10	<10
2132	Not detected	Not detected	Not applicable
2247	NOT DETECTED	NOT DETECTED	----
2250	----	----	----
2265	----	----	----
2293	----	----	----
2310	not detected	not detected	not detected
2311	Not Detected	Not Detected	Not Detected
2330	Not applicable	Not applicable	Not applicable
2352	ND	ND	ND
2358	not detected	not detected	not detected
2363	----	----	----
2365	<1.0	<1.0	----
2370	<2	<2	<2
2375	----	----	----
2386	----	----	----
2390	not analyzed	not analyzed	not analyzed
2455	----	----	----
2561	Not Detected	Not Detected	----
2590	----	----	----
2602	----	----	----
2695	not detected	not analyzed	not analyzed
2711	not detected	not analyzed	----
2723	1	Not detected	Not analyzed
2737	----	----	----
2756	----	----	----
2806	< 10	----	----
2826	not detected	not determined	NA
2959	----	----	----
3116	----	----	----
3154	----	----	----
3172	< 5	----	----
3197	<10	<10	----
3210	<40	----	----
3228	----	----	----
3237	----	----	----

APPENDIX 3 Analytical Details

lab	ISO 17025 accr.	sample preparation	sample intake (g)
551	Yes	Used as received	1g
623	Yes	Further cut	1 gram
2115	No	Used as received	1 g
2129	Yes	Used as received	0.5g
2132	No	Used as received	1 gram
2247	---	---	
2250	Yes	Used as received	0,5g
2265	No	Used as received	0,5
2293	---	---	
2310	Yes	Used as received	1
2311	No	Further cut	0.5
2330	No	Further cut	0.5 g
2352	Yes	Used as received	1g
2358	Yes	Used as received	1 gram
2363	---	---	
2365	Yes	Used as received	1.0g
2370	Yes	Used as received	0.5 g
2375	Yes	Further cut	0.5 gram
2386	Yes	Used as received	0.500
2390	Yes	Used as received	0.5 gram
2455	Yes	Used as received	# A: 1.0590 g; # B: 1.1133 g
2561	No	Used as received	1g
2590	Yes		1g
2602	Yes	Used as received	0,75 g / 20ml Acetonitril
2695	Yes	Used as received	1g
2711	No	Used as received	1.026
2723	No	Used as received	1g
2737	Yes	Used as received	0.5g
2756	Yes	Used as received	
2806	Yes	Further cut	
2826	Yes	Used as received	0.5gram
2959	Yes	Used as received	0.5g
3116	No	Used as received	0.5 gram
3154	Yes	Used as received	1
3172	---	---	
3197	Yes	Used as received	0,5 g
3210	Yes	Used as received	1.000
3228	Yes	Used as received	0.5
3237	Yes	Used as received	2

APPENDIX 4

Number of participants per country

1 lab in BRAZIL
1 lab in CAMBODIA
1 lab in ETHIOPIA
1 lab in FRANCE
6 labs in GERMANY
1 lab in GUATEMALA
4 labs in HONG KONG
3 labs in INDIA
1 lab in INDONESIA
6 labs in ITALY
6 labs in P.R. of CHINA
1 lab in PAKISTAN
1 lab in SWITZERLAND
1 lab in TAIWAN
3 labs in TURKEY
1 lab in U.S.A.
1 lab in UNITED KINGDOM

APPENDIX 5

Abbreviations

C	= final test result after checking of first reported suspect test result
D(0.01)	= outlier in Dixon's outlier test
D(0.05)	= straggler in Dixon's outlier test
G(0.01)	= outlier in Grubbs' outlier test
G(0.05)	= straggler in Grubbs' outlier test
DG(0.01)	= outlier in Double Grubbs' outlier test
DG(0.05)	= straggler in Double Grubbs' outlier test
R(0.01)	= outlier in Rosner's outlier test
R(0.05)	= straggler in Rosner's outlier test
E	= calculation difference between reported test result and result calculated by iis
W	= test result withdrawn on request of participant
ex	= test result excluded from statistical evaluation
n.a.	= not applicable
n.e.	= not evaluated
n.d.	= not detected
fr.	= first reported
f+?	= possibly a false positive test result?
f-?	= possibly a false negative test result?

Literature

- 1 iis Interlaboratory Studies, Protocol for the Organisation, Statistics & Evaluation, June 2018
- 2 ISO5725:86
- 3 ISO5725 parts 1-6:94
- 4 ISO13528:05
- 5 M. Thompson and R. Wood, J. AOAC Int, 76, 926, (1993)
- 6 W.J. Youden and E.H. Steiner, Statistical Manual of the AOAC, (1975)
- 7 P.L. Davies, Fr. Z. Anal. Chem, 331, 513, (1988)
- 8 J.N. Miller, Analyst, 118, 455, (1993)
- 9 Analytical Methods Committee, Technical Brief, No 4, January 2001
- 10 P.J. Lowthian and M. Thompson, The Royal Society of Chemistry, Analyst, 127, 1359-1364, (2002)
- 11 W. Horwitz and R. Albert, J. AOAC Int, 79.3, 589-621, (1996)
- 12 Bernard Rosner, Percentage Points for a Generalized ESD Many-Outlier Procedure, Technometrics, 25(2), 165-172, (1983)
- 13 iis memo 1601 Precision data of OPP/PCP in textile (2016)